

Thermobaric Effect on Melt-Textured $\text{MBa}_2\text{Cu}_3\text{O}_{7-\delta}$ ($\text{M} = \text{Y}, \text{Nd}$)

T. Prikhna^{a,1}, W. Gawalek^b, V. Moshchil^a, R. Viznichenko^c, F. Sandiumenge^d,
V. Melnikov^e, P. Shaetzle^f, P. Nagorny^a, A. Surzhenko^b, S. Dub^a, Ch. Wende^b

^a*Institute for Superhard Materials, 2, Avtozavodskaya Str., Kiev 254074, Ukraine*

^b*Institut fuer Physikalische Hochtechnologie e.V., 10, Winzerlaer, Jena D-07745, Germany*

^c*Institute of Metal Physics, 36, Vernadsky Ave., Kiev, 252142, Ukraine*

^d*Instituto de Ciencia de Materiales de Barcelona, Bellaterra E-08193, Catalunya, Espana*

^e*Institute of Geochemistry, Mineralogy and Ore-Formation, 34, Palladin Ave., Kiev 252142, Ukraine*

^f*Institut fuer Festkoerper- und Werkstofforschung, Winterbergstrasse 28, D-01277 Dresden, Germany*

Abstract

The effect of a short (10–30 min) thermobaric action (in the 1–5 GPa pressure and 700–1300°C temperature range) on the structure, superconductive and mechanical properties of melt-textured $\text{MBa}_2\text{Cu}_3\text{O}_{7-\delta}$ ($\text{M} = \text{Y}, \text{Nd}$) or MT-MBCO have been studied. The existence has been established of pressure-temperature-time conditions (2 GPa, 800°C for 30 min and 900–950°C for 15 min for MT-YBCO; 5 GPa, 850–900°C for 15 min for MT-NdBCO) the treatment under which allows superconductive properties of the materials (because of the contact with zirconia and high pressure) to be preserved or improved, mechanical characteristics increased and the materials condensed.

Key words: high temperature superconductors; melt-textured $\text{MBa}_2\text{Cu}_3\text{O}_{7-\delta}$; critical current density; high pressure; thermobaric treatment

1. Introduction

Among known bulk high-temperature superconductive materials, MT-MBCO ($\text{M} = \text{Y}, \text{Nd}$) possesses the highest level of cryomagnetic properties, which enables us to construct HTSC electromotors with massive MT-YBCO rotors with output power of about 19 kW at 3000 rpm [1]. The structure of MT-MBCO samples consists of a few large textured grains or magnetic domains of $\text{MBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (M123) with finely dispersed small

inclusions of the non-superconductive Y_2BaCuO_5 (Y211) phase or $\text{Nd}_4\text{Ba}_2\text{Cu}_2\text{O}_{10}$ (Nd422) for $\text{M} = \text{Y}$ or Nd , respectively. M123 grains are well oriented relative to each other, so that their *ab*-planes and *c*-axes are almost parallel. The presence of Y211 or Nd422 grains, which can serve as pinning centers in the M123 matrix, leads to an increase in critical current density. A melt-textured material usually has micro- and macrocracks in the structure and pores (its density is 85–90 % from the theoretical one). The further increase of material density and improvement of mechanical properties are of great importance.

¹ Corresponding author. Present address: Institute for Superhard Materials, 2, Avtozavodskaya Str., Kiev 254074, Ukraine, E-mail: frd@ismanu.kiev.ua

2. Method, results and discussion

High pressure - high temperature conditions (HP-HT) have been created in recessed-anvil-type HP apparatuses [2], where the treated sample has been surrounded with precompacted monoclinic zirconia. Fig. 1 and 2 present the variations of unit cell parameters and critical current density (j_c) versus treatment conditions for MT-MBCO samples. With an increase in treatment temperature the tetragonal Y123 structure forms due to the increase of oxygen content up to more than 7

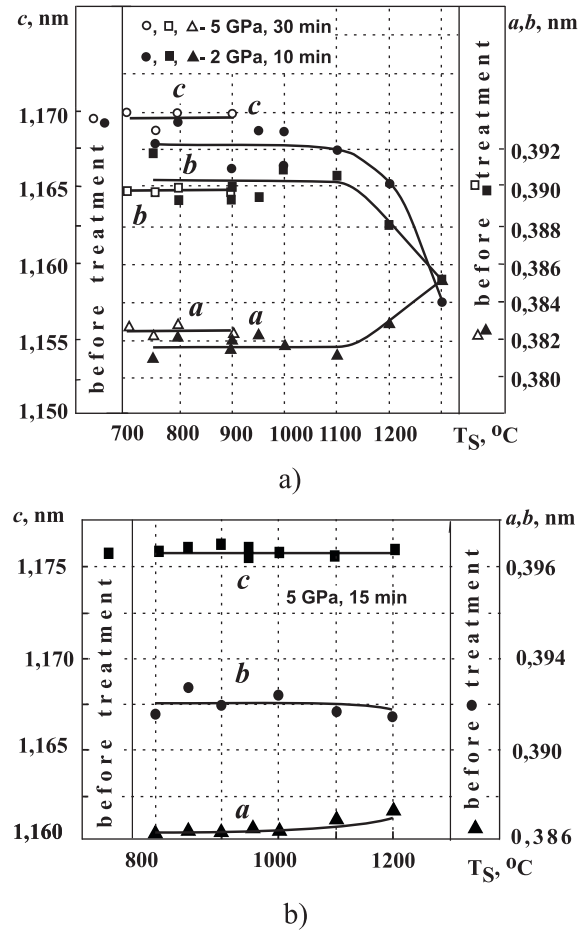


Fig. 1. Crystallographic parameters a , b , c versus treatment temperature (T_s) before and after HP-HT treatment of (a) YBa₂Cu₃O_{7-δ} -phase of MT-YBCO, treated at 2 and 5 GPa (b) NdBa₂Cu₃O_{7-δ} -phase of MT-NdBCO, treated under 5 GPa

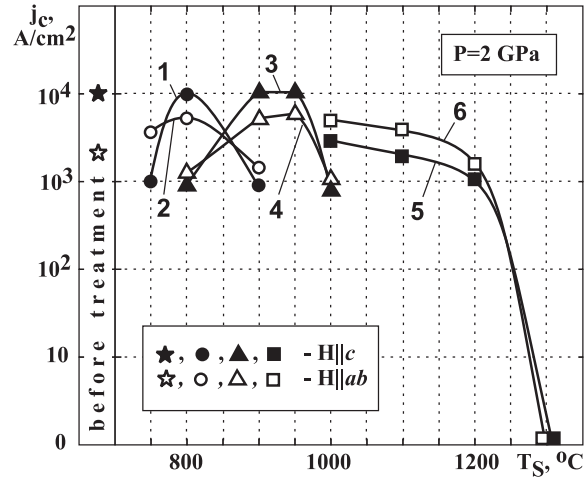


Fig. 2. Schematic representation of the critical current density variations at 77 K and zero magnetic field (H) of YBa₂Cu₃O_{7-δ} -phase of MT-YBCO vs. the treatment temperature (T_s) and time. Samples were treated at 2 GPa for 30 min (curves 1, 2), 15 min (3,4), and 10 min (5,6); solid dots — $H||c$, open dots — $H||ab$.

oxygen atoms per unit cell [2] as witnessed by a decrease in the c -parameter. After optimal HP-HT treatment the j_c in ab -plane of MT-MBCO ($M = Y, Nd$) was unchanged: 10⁴ A/cm², but some increase in j_c along c -axis have been observed, which may be the result of densification and the increase in dislocation density (for MT-YBCO from 10⁸ up to 10¹² cm⁻¹ in (001) planes). Materials density increased from 5.7 to 6.3 g/cm³ and from 5.5 to 6.64 g/cm³, Vickers microhardness from 3.4 to 5.3 GPa (4.91-N load) and from 4.9 to 5.9 GPa (1.96-N load) for $M = Y$ and Nd , respectively.

References

- [1] W. Gawalek, T. Habisreuther, T. Strasser, M. Wu, D. Lizkendorf, K.V. Ilushin, V.T. Penkin, L.K. Kovalev, J. Beest and B. Oswald, in Program and Abstracts of XI Trilateral German/Russian/Ukrainian Seminar on High-Temperature- Superconductivity, September 28-30, 1998 (Goettingen, Germany, 1998) p. 14.
- [2] T.A. Prikhna, V.S. Melnikov, V.V. Kovylyayev and V.V. Moshchil, J. Mat. Sci. 30 (1995) 3662.